

One-Step Reforming of CO₂ and CH₄ into High-Value Liquid Chemicals and Fuels at Room Temperature by Plasma-Driven Catalysis

Li Wang, Yanhui Yi, Chunfei Wu, Hongchen Guo, and Xin Tu*

Abstract: The conversion of CO₂ with CH₄ into liquid fuels and chemicals in a single-step catalytic process that bypasses the production of syngas remains a challenge. In this study, liquid fuels and chemicals (e.g., acetic acid, methanol, ethanol, and formaldehyde) were synthesized in a one-step process from CO₂ and CH₄ at room temperature (30 °C) and atmospheric pressure for the first time by using a novel plasma reactor with a water electrode. The total selectivity to oxygenates was approximately 50–60%, with acetic acid being the major component at 40.2% selectivity, the highest value reported for acetic acid thus far. Interestingly, the direct plasma synthesis of acetic acid from CH₄ and CO₂ is an ideal reaction with 100% atom economy, but it is almost impossible by thermal catalysis owing to the significant thermodynamic barrier. The combination of plasma and catalyst in this process shows great potential for manipulating the distribution of liquid chemical products in a given process.

Chemical transformations of CO₂ into value-added chemicals and fuels have been regarded as a key element for creating a sustainable low-carbon economy in the chemical and energy industry. A particularly significant route that is currently being developed for CO₂ utilization is catalytic CO₂ hydrogenation. This process can produce a range of fuels and chemicals, including CO, formic acid, methanol, hydrocarbons, and alcohols; however, high H₂ consumptions (CO₂ + 3H₂ → CH₃OH + H₂O) and high operating pressures (ca. 30–300 bar) are major challenges associated with this process.

Instead of using H₂, the direct conversion of CO₂ with CH₄ (dry reforming of methane, DRM) into liquid fuels and chemicals (e.g., acetic acid) represents another promising route for both CO₂ valorization and CH₄ activation. CH₄ is an ideal H supplier to replace H₂ in CO₂ hydrogenation as CH₄ has a high H density and is available from a range of sources (e.g., natural gas, shale gas, biogas, and flared gas). Moreover, it is an inexpensive carbon source that can increase the atom utilization of CO₂ hydrogenation owing to the stoichiometric ratio of C and O atoms, as well as reduce the formation of water.

Recently, Ge and co-workers investigated the direct C–C coupling of CO₂ and CH₄ to form acetic acid on a Zn-doped ceria catalyst by density functional theory (DFT) modeling;^[1] this is an attractive route as the direct conversion of CO₂ and CH₄ into acetic acid is a reaction with 100% atom economy [Equation (1)]. However, this reaction is thermodynamically



unfavorable under practical conditions. The conventional indirect catalytic process often proceeds through two steps (Scheme 1): 1) DRM to produce syngas (CO and H₂) at high temperatures (> 700 °C), and 2) conversion of syngas into liquid fuels and chemicals at high pressures. This indirect route for CO₂ valorization and CH₄ activation is inefficient as the DRM process for syngas production is highly endothermic and requires high temperatures and energy input [Equation (2)]. Catalyst deactivation due to carbon deposition is




[*] Dr. L. Wang, Dr. X. Tu
Department of Electrical Engineering and Electronics
University of Liverpool
Liverpool, L69 3GJ (UK)
E-mail: xin.tu@liv.ac.uk

Dr. Y. Yi, Prof. H. Guo
State Key Laboratory of Fine Chemicals
School of Chemical Engineering, Dalian University of Technology
Dalian, 116024 (P. R. China)

Dr. C. Wu
School of Engineering, University of Hull
Hull, HU6 7RX (UK)

Supporting information and the ORCID identification number(s) for the author(s) of this article can be found under:
<https://doi.org/10.1002/anie.201707131>.

© 2017 The Authors. Published by Wiley-VCH Verlag GmbH & Co. KGaA. This is an open access article under the terms of the Creative Commons Attribution License, which permits use, distribution and reproduction in any medium, provided the original work is properly cited.

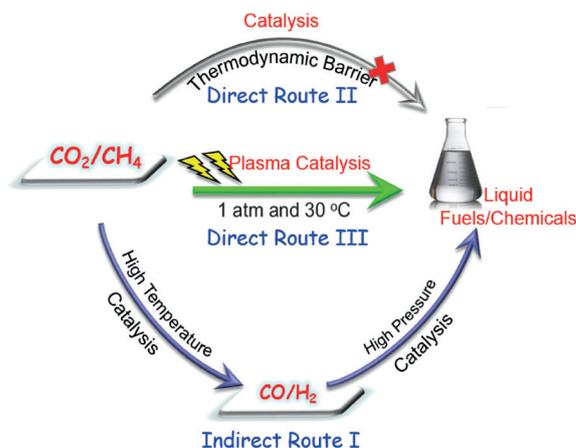

Scheme 1. Direct and indirect processes for the conversion of CO₂ and CH₄ into liquid fuels and chemicals.

another challenge impacting the use of this reaction on a commercial scale. It is almost impossible to directly convert two stable and inert molecules (CO_2 and CH_4) into liquid fuels or chemicals in a one-step catalytic process bypassing the production of syngas. A stepwise method was proposed to convert CO_2 and CH_4 into acetic acid over Cu/Co-based catalysts,^[2] Pd/C, Pt/ Al_2O_3 ,^[3] Pd/ SiO_2 , and Rh/ SiO_2 ^[4] by heterogeneous catalysis. The catalyst was first exposed to CH_4 , forming CH_x species on the catalyst surface. Subsequently, the feed gas was changed from CH_4 to CO_2 , and acetic acid was formed through the reaction of CO_2 with CH_x over the catalyst. This indirect process is complicated by the periodic change of reactants and the product collection.^[5]

Non-thermal plasmas (NTPs) offer a unique way to enable thermodynamically unfavorable chemical reactions at low temperatures owing to the non-equilibrium character. The overall gas temperature in an NTP remains low while the generated electrons are highly energetic with a typical electron temperature of 1–10 eV, which is sufficient to activate inert molecules (e.g., CO_2 and CH_4) into reactive species, including radicals, excited atoms, molecules, and ions. These energetic species are capable of initiating a variety of chemical reactions. Although much effort has been devoted to the use of NTPs for the degradation of gas pollutants, far less has been done with regard to their use in the synthesis of fuels and chemicals.^[6] Previous work on DRM with NTPs mainly focused on syngas production,^[7] while very limited efforts have been devoted to the challenging one-step conversion of CH_4 and CO_2 into liquid fuels and chemicals.^[8,9] A few groups have reported on the formation of trace oxygenates (e.g., alcohols and acids) as side products in plasma DRM for syngas production.^[10] Thus far, the use of NTPs for the direct conversion of CO_2 and CH_4 into oxygenates has resulted in poor selectivities and yields.

Herein, we describe the development of a novel dielectric barrier discharge (DBD) reactor with a ground water electrode (see the Supporting Information, Schemes S1 and S2) for the one-step conversion of CO_2 and CH_4 into oxygenates at room temperature (30 °C) and atmospheric pressure. This setup is unique and has not been reported previously. Figure 1 shows that no reaction occurred in the “catalyst only” mode at 30 °C without plasma. However, the use of an NTP enabled this thermodynamically unfavorable reaction to occur at room temperature and resulted in the production of liquid chemicals, including acetic acid, methanol, ethanol, and acetone, with acetic acid being the major product. Trace amounts of formic acid, propanol, and butanol were also detected in the condensed liquid. In the plasma process without a catalyst (“plasma only”), a total liquid selectivity of 59.1% was achieved with selectivities of 33.7%, 11.9%, 11.9%, and 1.6% for acetic acid, ethanol, methanol, and acetone, respectively (Figure 1a). The CO selectivity was only about 20.0% (Figure 1b), and the CH_4 and CO_2 conversions amounted to approximately 18.3% and 15.4%, respectively (Figure 1c).

Combining the plasma process with a catalyst shows great potential for manipulating the production of different oxygenates under ambient conditions. Clearly, packing the Cu/ $\gamma\text{-Al}_2\text{O}_3$ catalyst in the DBD enhanced the selectivity for acetic

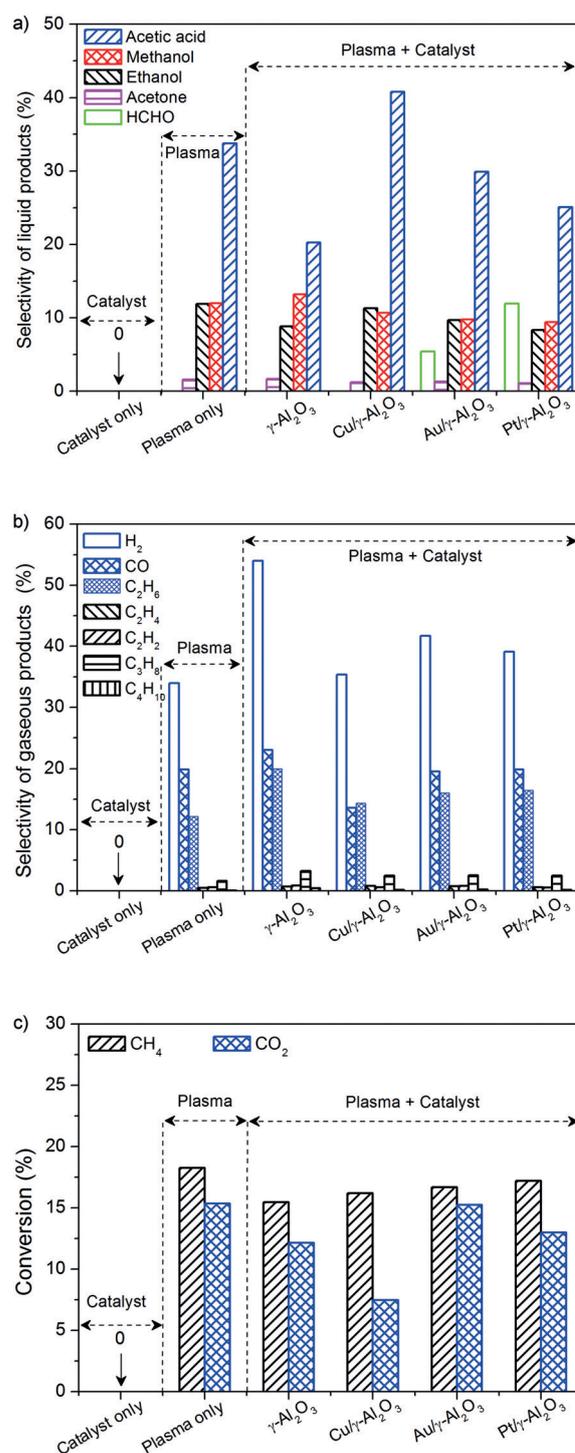


Figure 1. Effect of operating modes and catalysts on the reaction: a) Selectivities for oxygenates, b) selectivities for gaseous products, c) conversion of CH_4 and CO_2 (total flow rate 40 mL min^{-1} , discharge power 10 W, catalyst ca. 2 g).

acid to 40.2%, compared to the plasma-only mode and the plasma reaction using $\gamma\text{-Al}_2\text{O}_3$ only (20.2%). Acetic acid was the major product regardless of the catalyst used, followed by methanol and ethanol (Figure 1a). HCHO was formed only when the supported noble metal catalysts were used in the


plasma reaction, and the Pt/ γ -Al₂O₃ catalyst showed the highest selectivity to HCHO. Compared to the plasma-only mode, placing the catalysts in the DBD gave similar gaseous product distributions, with H₂, CO, and C₂H₆ being the major gaseous products (Figure 1 b). However, combining the NTP with the catalysts enhanced the H₂ selectivity by 10–20% (except for Cu/ γ -Al₂O₃), and slightly increased C₂H₆ production, but had a weak effect on the selectivity for CO (except for Cu/ γ -Al₂O₃, which decreased CO selectivity to 13.5%) and other C_xH_y (i.e., C₂H₂, C₂H₄, C₂H₆, C₃H₈, and *n*-C₄H₁₀). In addition, compared to the plasma-only mode, the conversion of CO₂ and CH₄ slightly decreased with packing catalysts. This phenomenon can be attributed to the change in discharge behavior induced by the catalyst, which had a negative effect on the reaction (Figure S1). Interestingly, C₆H₁₂O₄ (CAS No. 49653-17-0) was found on the inner reactor wall in the plasma-catalyst mode (Figure S2). These results demonstrate the feasibility of using NTPs for the direct conversion of CH₄ and CO₂ into higher-value liquid fuels and chemicals in a single-step process under ambient conditions, bypassing the formation of syngas.

To understand the formation of the liquid chemicals, optical emission spectroscopy (OES) was used to investigate the species produced in the CH₄/CO₂ DBD (Figure 2). H _{α} and O atomic lines and CH, C₂, CO₂⁺, CO₂, and CO bands were identified in the emission spectra of the DBD, with CO, CH, and H being the major ones (Table S2).

CO is mainly derived from reactions S1–S3 (Table S3) in the DBD. Our simulation showed that electron-impact CO₂ reactions produced about 95% vibrationally excited CO₂ (CO₂(v)) compared to electronically excited CO₂ as shown in Figure S3 and Table S4. O radicals generated from CO₂ dissociation can attack CO₂(v) molecules to produce CO (S1 and S2).^[11] Different from CH, CH₃ derived from CH₄ dissociation cannot be detected by OES, but recent simulations revealed that electron-impact dissociation of CH₄ leads to 79% CH₃ formation and only 15% and 5% CH₂ and CH, respectively.^[12] Therefore, CH₃ is the dominant species in the CH₄/CO₂ DBD. In addition to electrons (S4 in Table S3),

reactive species such as OH, O, and H can also react with CH₄ to produce CH₃ radicals (S5–S7) in the CH₄/CO₂ DBD. Additionally, OH is an important species, especially for alcohol formation. In the CH₄/CO₂ DBD, OH could be produced indirectly by reactions S8–S13, with S8 and S9 as the major channels based on the reaction rate coefficients and *E_a*.^[13] Special attention was given to S10, although a very low reaction rate coefficient of 1.4×10^{-29} cm³ molecule⁻¹ s⁻¹ and a high *E_a* value of 111 kJ mol⁻¹ were determined for ground-state CO₂ reacting with an H radical to produce an OH radical; this reaction (S10) can be accelerated by using CO₂(v) instead of ground-state CO₂.^[14] and the use of vibrationally excited reagents is most effective in overcoming the activation barrier of the endothermic reaction.^[14,15] Thus the reaction CO₂(v) + H → CO + OH could be one of the major routes for OH formation under these conditions as CO₂ is mainly present in vibrationally excited states (Figure S3).

Based on the analysis of the gaseous and condensed liquid products and the OES results, CO, CH₃, and OH radicals are the key species in the CH₄/CO₂ plasma reaction. Therefore, possible reaction pathways for the formation of acetic acid, methanol, and ethanol under these conditions are proposed in Scheme 2.

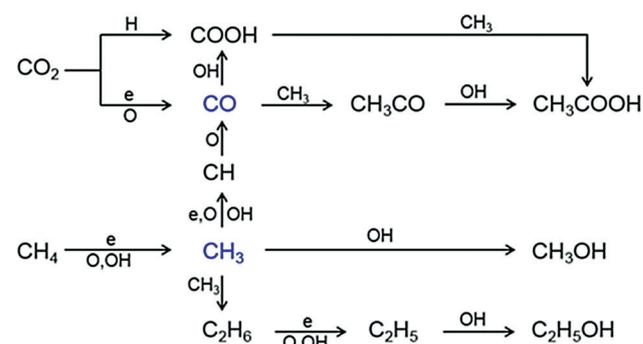

Scheme 2. Possible reaction pathways for the formation of CH₃COOH, CH₃OH, and C₂H₅OH in the direct reforming of CH₄ and CO₂ with DBD.

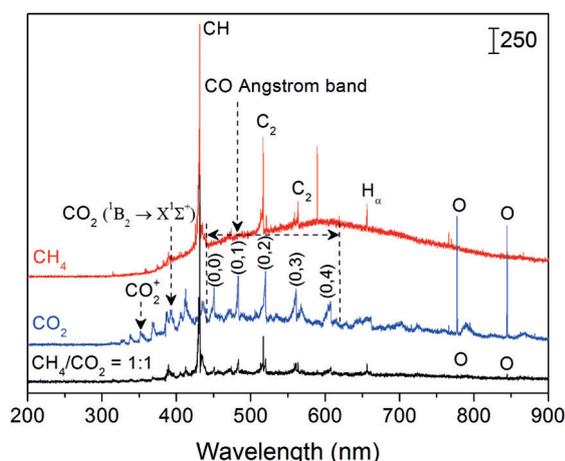


Figure 2. Optical emission spectra of CH₄, CO₂, and CH₄/CO₂ plasmas (total flow rate 40 mL min⁻¹, CH₄/CO₂ ratio 1:1, discharge power 10 W, exposure time 2 s).

Two possible reaction pathways could contribute to the formation of acetic acid. CO can react with a CH₃ radical to form an acetyl radical (CH₃CO) by reaction S14 in Table S3 with a low energy barrier of 28.77 kJ mol⁻¹,^[16] followed by recombination with OH to produce acetic acid in reaction S15 with no energy barrier^[10g] (see also Figures 3 and S4). Clearly, the selectivity to acetic acid increases initially and then decreases with the CH₄/CO₂ ratio, with optimal acetic acid formation at a CH₄/CO₂ ratio of 1:1. Correspondingly, the relative intensities of the CO band head and the O atomic line increased with a decrease in the CH₄/CO₂ ratio from 3:1 to 1:2 while that of the CH band head increased (Figure S4). This suggests that decreasing the CH₄/CO₂ molar ratio decreases the generation of CH₃ radicals, but increases OH formation. A similar mechanism of acetic acid formation has been proposed on the basis of DFT modeling^[10g] and by Eliasson and co-workers.^[10i] In addition, direct coupling of CH₃ and carboxyl radicals (COOH) could also form acetic acid by

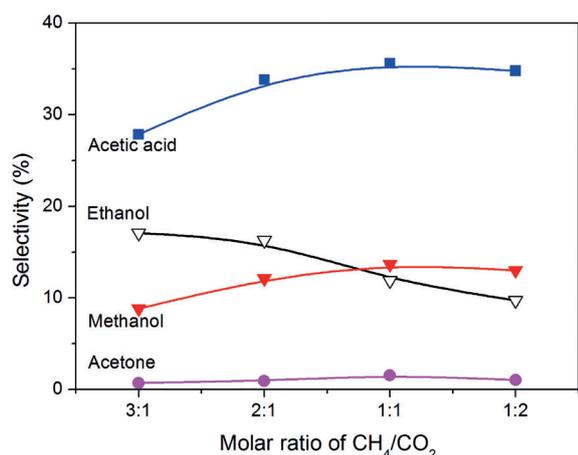


Figure 3. Effect of the CH₄/CO₂ molar ratio on the selectivity for oxygenates without a catalyst (total flow rate 40 mL min⁻¹, discharge power 10 W).

reaction S16, while COOH radicals may be formed from reactions S17 and S18 in Table S3.^[10g]

Decreasing the CH₄/CO₂ molar ratio decreased the generation of CH₃ radicals, but increased OH formation (Figure S4). Simultaneously, the formation of CH₃OH increased initially with a decrease in the CH₄/CO₂ molar ratio and reached a peak at a CH₄/CO₂ molar ratio of 1:1. By contrast, the formation of C₂H₅OH decreased continuously as the CH₄/CO₂ molar ratio was decreased (Figure 3). These findings suggest that the production of CH₃OH mainly depends on the generation of both CH₃ and OH radicals while the formation of C₂H₅OH is more sensitive to the presence of CH₃ radicals in the plasma reaction as C₂H₅OH formation requires twice the amount of CH₃ radicals in comparison to the formation of CH₃OH. As shown in Scheme 2, CH₃OH can be directly formed from the coupling of CH₃ and OH radicals with a high rate coefficient (S19 in Table S3),^[17] while C₂H₅OH formation requires several elementary reactions (S20–S24). The recombination of a CH₃ radical with itself forms C₂H₆ (S20),^[18] which is followed by dehydrogenation to form a C₂H₅ radical by reactions S21–S23, with S21 as the primary reaction according to the reaction rates.^[13d,19] The C₂H₅ radical finally recombines with OH to form C₂H₅OH with a high rate coefficient of 9.34 × 10⁻¹¹ cm³ molecule⁻¹ s⁻¹ (S24).^[20]

Clearly, adding catalysts to the plasma reaction influences the distribution of the formed oxygenates, especially for the formation of HCHO after addition of the Pt and Au catalysts, revealing the occurrence of surface reactions in addition to plasma gas phase reactions.^[21] In traditional catalysis, CO hydrogenation, CH₃OH oxidation, and methylene (CH₂) oxidation can lead to the generation of HCHO over noble-metal catalysts.^[22] In this plasma process, adding noble-metal catalysts in the plasma had almost no influence on the CO selectivity, but decreased the selectivity for CH₃OH, C₂H₅OH, and CH₃COOH and increased the selectivity for HCHO and C₂H₆ (Figure 1a). Considering the major species that are present in the CH₄/CO₂ DBD, CH_x (x = 4, 3, and 2) could be the primary source for HCHO formation by

oxidation reactions. Namely, CH_x in the gas phase could be adsorbed onto the surface of the catalyst to form HCHO by the oxidation of CH_{2,ad} (CH_{x,ad} + O, H, OH → CH_{2,ad}) and to produce C₂H₆ by self-recombination of CH₃ radicals instead of converting CH₃ into CH₃OH, C₂H₅OH, and CH₃COOH. This could explain why the presence of the Au and Pt catalysts in the plasma decreased the formation of CH₃OH, C₂H₅OH, and CH₃COOH, but enhanced the production of C₂H₆ and HCHO (Figures 1a and b). Possible pathways for the formation of the major oxygenates on the catalyst surface are proposed in Scheme S3. In addition, catalyst characterization (Figures S5–S8) suggested that the metal particle size and interactions between metal and support are not determining factors for the reaction performance (Figure 1), whereas the strength of the bonding of adsorbed intermediates to the catalyst surface, that is, the oxygen adsorption energy (ΔE_O), could be a good activity descriptor towards the formation of different products in DRM.^[23]

In conclusion, the one-step room-temperature synthesis of liquid fuels and chemicals from the direct reforming of CO₂ with CH₄ has been achieved by using a novel atmospheric-pressure DBD reactor. The total selectivity for liquid chemicals was approximately 50–60%, with acetic acid as the major product. The CH₄/CO₂ molar ratio and the type of catalyst can be used to manipulate the production of different oxygenates. These results clearly show that non-thermal plasmas can be used to overcome the thermodynamic barrier for the direct transformation of CH₄ and CO₂ into a range of strategically important platform chemicals, especially for the production of acetic acid with 100% atom economy. Additionally, combining the DBD with noble-metal catalysts produced formaldehyde, which cannot be generated in the same plasma reaction without a catalyst. This finding suggests that new research should be directed at designing a catalyst with high selectivity towards a desirable product.

Acknowledgements

Support of this work by the EPSRC SUPERGEN Hydrogen & Fuel Cell (H2FC) Programme (EP/J016454/1) ECR Project (Ref. EACPR PS5768) is gratefully acknowledged.

Conflict of interest

The authors declare no conflict of interest.

Keywords: carbon dioxide · heterogeneous catalysis · methane · plasma chemistry · reforming

How to cite: *Angew. Chem. Int. Ed.* **2017**, *56*, 13679–13683
Angew. Chem. **2017**, *129*, 13867–13871

- [1] Y. Zhao, C. Cui, J. Han, H. Wang, X. Zhu, Q. Ge, *J. Am. Chem. Soc.* **2016**, *138*, 10191–10198.
- [2] W. Huang, K. C. Xie, J. P. Wang, Z. H. Gao, L. H. Yin, Q. M. Zhu, *J. Catal.* **2001**, *201*, 100–104.
- [3] E. M. Wilcox, G. W. Roberts, J. J. Spivey, *Catal. Today* **2003**, *88*, 83–90.

- [4] Y.-H. Ding, W. Huang, Y.-G. Wang, *Fuel Process. Technol.* **2007**, *88*, 319–324.
- [5] a) A. A. Olajire, *J. CO₂ Util.* **2013**, *3–4*, 74–92; b) A. Otto, T. Grube, S. Schiebahn, D. Stolten, *Energy Environ. Sci.* **2015**, *8*, 3283–3297; c) I. Dimitriou, P. García-Gutiérrez, R. H. Elder, R. M. Cuéllar-Franca, A. Azapagic, R. W. Allen, *Energy Environ. Sci.* **2015**, *8*, 1775–1789; d) M.-S. Fan, A. Z. Abdullah, S. Bhatia, *ChemCatChem* **2009**, *1*, 192–208; e) D. Pakhare, J. Spivey, *Chem. Soc. Rev.* **2014**, *43*, 7813–7837; f) V. Havran, M. P. Dudukovic, C. S. Lo, *Ind. Eng. Chem. Res.* **2011**, *50*, 7089–7100.
- [6] C. E. Stere, J. A. Anderson, S. Chansai, J. J. Delgado, A. Goguet, W. G. Graham, C. Hardacre, S. Taylor, X. Tu, Z. Wang, *Angew. Chem. Int. Ed.* **2017**, *56*, 5579–5583; *Angew. Chem.* **2017**, *129*, 5671–5675.
- [7] a) W.-C. Chung, M.-B. Chang, *Renewable Sustainable Energy Rev.* **2016**, *62*, 13–31; b) A. Lebouvier, S. A. Iwarere, P. d'Argenlieu, D. Ramjugernath, L. Fulcheri, *Energy Fuels* **2013**, *27*, 2712–2722; c) X. Tao, M. Bai, X. Li, H. Long, S. Shang, Y. Yin, X. Dai, *Prog. Energy Combust. Sci.* **2011**, *37*, 113–124; d) X. Tu, J. C. Whitehead, *Int. J. Hydrogen Energy* **2014**, *39*, 9658–9669.
- [8] J.-J. Zou, Y.-p. Zhang, C.-J. Liu, Y. Li, B. Eliasson, *Plasma Chem. Plasma Process.* **2003**, *23*, 69–82.
- [9] M. Scapinello, L. M. Martini, P. Tosi, *Plasma Processes Polym.* **2014**, *11*, 624–628.
- [10] a) K. Kozlov, P. Michel, H.-E. Wagner, *Plasmas Polym.* **2000**, *5*, 129–150; b) G. R. Dey, T. N. Das, *Plasma Chem. Plasma Process.* **2006**, *26*, 495–505; c) A. Gómez-Ramírez, V. J. Rico, J. Cotrino, A. R. González-Eliphe, R. M. Lambert, *ACS Catal.* **2014**, *4*, 402–408; d) V. Goujard, J.-M. Tatibouët, C. Batiot-Dupeyrat, *Appl. Catal. A* **2009**, *353*, 228–235; e) J. Sentek, K. Krawczyk, M. Młotek, M. Kalczewska, T. Kroker, T. Kolb, A. Schenk, K.-H. Gericke, K. Schmidt-Szałowski, *Appl. Catal. B* **2010**, *94*, 19–26; f) K. Krawczyk, M. Młotek, B. Ulejczyk, K. Schmidt-Szałowski, *Fuel* **2014**, *117*, 608–617; g) L. M. Martini, G. Dilecce, G. Guella, A. Maranzana, G. Tonachini, P. Tosi, *Chem. Phys. Lett.* **2014**, *593*, 55–60; h) C. Liu, J. Wang, Y. Wang, B. Eliasson, *Fuel Chem. Div. Prepr.* **2003**, *48*, 268; i) J. G. Wang, C. J. Liu, B. Eliasson, *Energy Fuels* **2004**, *18*, 148–153.
- [11] A. Fridman, *Plasma Chemistry*, Cambridge University Press, **2008**.
- [12] C. De Bie, B. Verheyde, T. Martens, J. van Dijk, S. Paulussen, A. Bogaerts, *Plasma Processes Polym.* **2011**, *8*, 1033–1058.
- [13] a) J. Murrell, J. Rodriguez, *J. Mol. Struct. THEOCHEM* **1986**, *139*, 267–276; b) D. C. Robie, S. Arepalli, N. Presser, T. Kitsopoulos, R. J. Gordon, *J. Chem. Phys.* **1990**, *92*, 7382–7393; c) W. Tsang, R. Hampson, *J. Phys. Chem. Ref. Data* **1986**, *15*, 1087–1279; d) D. Baulch, C. Cobos, R. Cox, C. Esser, P. Frank, T. Just, J. Kerr, M. Pilling, J. Troe, R. Walker, *J. Phys. Chem. Ref. Data* **1992**, *21*, 411–734; e) S. P. Karkach, V. I. Osherov, *J. Chem. Phys.* **1999**, *110*, 11918–11927.
- [14] V. Rusanov, A. Fridman, G. Sholin, *Phys. Usp.* **1981**, *24*, 447–474.
- [15] J. C. Polanyi, *Science* **1987**, *236*, 680–690.
- [16] D. Baulch, C. Cobos, R. Cox, P. Frank, G. Hayman, T. Just, J. Kerr, T. Murrells, M. Pilling, J. Troe, *J. Phys. Chem. Ref. Data* **1994**, *23*, 847–848.
- [17] A. W. Jasper, S. J. Klippenstein, L. B. Harding, B. Ruscic, *J. Phys. Chem. A* **2007**, *111*, 3932–3950.
- [18] R. Gomer, G. Kistiakowsky, *J. Chem. Phys.* **1951**, *19*, 85–91.
- [19] R. Atkinson, D. Baulch, R. Cox, R. Hampson, Jr., J. Kerr, M. Rossi, J. Troe, *J. Phys. Chem. Ref. Data* **1997**, *26*, 521–1011.
- [20] R. Sivaramakrishnan, M.-C. Su, J. Michael, S. Klippenstein, L. Harding, B. Ruscic, *J. Phys. Chem. A* **2010**, *114*, 9425–9439.
- [21] L. Wang, Y. Zhao, C. Liu, W. Gong, H. Guo, *Chem. Commun.* **2013**, *49*, 3787–3789.
- [22] a) Z.-Z. Lin, X. Chen, *Mater. Des.* **2016**, *107*, 82–89; b) S. Yin, Z. Wang, E. R. Bernstein, *Phys. Chem. Chem. Phys.* **2013**, *15*, 4699–4706; c) I. Sobczak, M. Kozłowska, M. Ziolk, *J. Mol. Catal. A* **2014**, *390*, 114–124; d) K. Czelej, K. Cwieka, J. C. Colmenares, K. J. Kurzydłowski, *Langmuir* **2016**, *32*, 7493–7502; e) J. Niu, J. Ran, R. Wang, X. Du, *Comput. Theor. Chem.* **2015**, *1067*, 40–47.
- [23] a) S. Kattel, B. Yan, Y. Yang, J. G. Chen, P. Liu, *J. Am. Chem. Soc.* **2016**, *138*, 12440–12450; b) M. Behrens, F. Studt, I. Kasatkin, S. Kühl, M. Hävecker, F. Abild-Pedersen, S. Zander, F. Girgsdies, P. Kurr, B.-L. Kniep, *Science* **2012**, *336*, 893–897; c) F. Studt, I. Sharafutdinov, F. Abild-Pedersen, C. F. Elkjær, J. S. Hummelshøj, S. Dahl, I. Chorkendorff, J. K. Nørskov, *Nat. Chem.* **2014**, *6*, 320–324.

Manuscript received: July 13, 2017

Accepted manuscript online: August 25, 2017

Version of record online: September 19, 2017